

**IN-SITU PHASE TRANSFORMATION
AND MICROSTRUCTURE OF REINFORCED
ALUMINIUM MATRIX COMPOSITES (AA-6061 T6+NiCr
Np) WITH AND WITHOUT TiC NANOPARTICLES**

DING WANWU^{1,2,*}, SAMI ULLAH KHAN^{1,2}, QUDRAT ULLAH KHAN³,
SHADAB KHAN⁴, ABID ALAM⁵, ARIF ULLAH⁶ AND HANIF ULLAH⁷

¹*State Key Laboratory of Advanced Processing and Recycling of Nonferrous Metals,
Lanzhou University of Technology, Lanzhou 730050, P.R. China,
e-mail: dingww@lut.cn*

²*School of Material Science and Engineering, Lanzhou University of Technology,
Lanzhou 730050, Gansu Province, P.R. China,
e-mail: engr.sami90@gmail.com*

³*Greater Bay Area Institute of Precision Medicine, Fudan University,
Nansha District, Guangzhou, Guangdong 511458, P.R. China,
e-mail: qukhan2@yahoo.com*

⁴*Department of Physics, Abbottabad University of Science & Technology,
Captain Akaash Rabbani Shaheed Road, Tehsil Havelian,
District Abbottabad, Khyber Pakhtunkhwa, Pakistan,
e-mail: shadabmarwat2013@gmail.com*

⁵*School of Physical Science and Technology, Lanzhou University,
Lanzhou-730030, Gansu P.R. China,
e-mail: abidalam174@gmail.com*

⁶*College of Chemistry and Chemical Engineering,
Northwest Normal University,
Lanzhou, Gansu 730070, People's Republic of China,
e-mail: arifullah4star@gmail.com*

⁷*School of Mechanical Science and Engineering,
Huazhong University of Science and Technology,
1037 Luoyu Road, Wuhan 430074 Hubei Province P.R. China,
e-mail: Hanifullah318@gmail.com*

* Corresponding author.

DOI: 10.7546/EngSci.LIX.22.02.02

Abstract. Aluminium composites are frequently employed in aircraft applications because of its exceptional qualities. Aluminium alumina composite was manufactured in-situ using the AA-6061 T6 matrix alloy and 3% age, 6% age (Nichrome) powder. Optical metallography, Image Analysis, and micro hardness tests were used to assess the in-situ composites. The specimens then liquid preheated at 550 °C for 3 hours and then aged at 180 °C for 7 hours to improve the durability in mechanical characteristics. In comparison with the as cast samples, the heat-treated samples showed significantly higher mechanical properties. AA-6061 T6 matrix composite reinforced with in-situ alumina particle with TiC was also studied for grain refining. The Al-4.5%Ti-1.5%C master alloy has been shown to be an effective grain refiner.

Keywords: in-situ, Nichrome Nanoparticle (NiCr Np), Metal Matrix Composites (MMCs), TiC Nanocomposites.

1. INTRODUCTION

Composites are composed of two or more constituent materials [1] that have considerably diverse mechanical, chemical, or physical characteristics yet stay distinct and separate on a macroscopic scale inside the final structure. The matrix of a metal matrix composite is often a lighter metal such as aluminum, magnesium, or titanium, and it offers a complaint support for the reinforcement [2, 3]. The matrix has reinforcing material inserted in it. The reinforcement is not necessarily employed for simply structural purposes (i.e., reinforcing the composite), but it may also be employed to alter physical qualities like wear resistance, friction coefficient, or thermal conductivity [4].

Metal Matrix Composites (MMCs) have become one of the most significant innovative materials [5], nowadays more interesting candidate due to their high mechanical characteristics. Because of their high specific modulus and strength, as well as excellent fatigue and creep resistance, aluminum-based metal matrix composites have gotten a lot of interest as building components in the aeronautical, automotive, and transportation sectors [6].

Aluminum matrix composites, for example, are frequently utilized because of their strong strength also at extreme temperatures, fracture toughness, lower density, high thermal conductivity, and great abrasion resistance [7]. In addition to traditional metal processing techniques, the emergence of diverse metal matrix composite systems has led to the creation of innovative analysis methods.

Since many studies have looked at MMCs, they have discovered that reducing the size of the reinforcement improves the characteristics. Some of the

disadvantages of metal matrix composites, such as low ductility, poor machinability, and decreased fracture toughness, may be solved by scaling down the particle size in metal matrix composites to NanoParticles (Nps). The inclusion of NPs in metals is predicted to result in considerable improvements due to recent developments in creating particles smaller than 100 nm. A nano composite is made up of two phases, at least one of which is nanoscale (less than 100 nm) in one dimension [8].

The in-situ technique is used to mix Nichrome particles (NiCr Np) into the aluminum melt [9]. The interaction between matrix and reinforcement in in-situ processing is free impurity pathway. The products are relatively stable and devoid of impurities. The melt environment will also shield the particles from oxidation. In order to produce an effective load transfer mechanism in nanocomposites, a strong connection between in-situ particles and the metal matrix is required. Furthermore, the in-situ produced reinforcing particles are smaller and have a more uniform distribution in the matrix, resulting in higher mechanical characteristics than ex-situ composites [10–12].

The goal of this study is to build and analyze an AA6061 matrix composite by adding an oxide bearing compound like Nichrome to it (NiCr Np). Optical metallography, Image Analysis, and microstructure are used to analyze the produced composites. Furthermore, an AA6061 matrix composite reinforced with NiCr Np particles is investigated both with and without inclusion of TiC.

2. METHODOLOGY OF PRODUCTION

2.1. Materials selection

The composite is prepared with AA-6061 T6 (aluminum alloy-Temper 6) in this study. AA-6061 is a precipitation-hardening aluminum alloy with the main alloying components magnesium and silicon. Optical emission spectroscopy was utilized to verify the chemical composition, and the true composition of the alloy employed in this investigation is given in Table 1. The matrix has the reinforcing material incorporated in it. As reinforcement, Nichrome (NiCr Np) powder is utilized. Furthermore, TiC, an Al-4.5%Ti-1.5%C master alloy, is employed as the grain refiner. In comparison with another master alloy, Al-4.5%Ti-1.5%C, the literature reveals that Al-4.5%Ti-1.5%C master alloy produces good results with the matrix alloy. Heated drops were decreased marginally with the addition of Al-4.5Ti-1.5C, but dramatically with the addition of Al-1Ti-3C. Due to massive TiAl_3 particles serving as strong connections during solidification, the inclusion of Al-5Ti-1C did not result in a reduction in warm drops.

Table 1. Component of elements in AA-6061 matrix alloy

Element	Aluminum	Magnesium	Silicon	Ferrum	Copper
Weight %	97.2	1	0.6	0.40	0.275
Element	Chromium	Nickel	Titanium	Manganese	
Weight %	0.195	0.125	0.125	0.080	

2.2. Composite fabrication technique

Resistance-heated ovens were used for alloy treatment. Ingots of AA-6061 were accessible. The needed quantity of AA 6061 alloy was extracted out from ingots and deposited in the furnace heater, which already housed the crucible. The alloy reached the liquid state when such temperature reached 660 °C the alloy begins to deteriorate at this temperature, whereas fluidity increases at 710 °C. The appropriate quantity was introduced to balance it due to the lack of magnesium content (as confirmed by optical emission spectroscopy) in AA 6061. The wettability of the molten was improved by adding 1% wt. magnesium to the solution. The alloy is then degassed using Hexachloroethane (C_2Cl_6) degassing tablets at an elevated temperature of around 710 °C the melt had been used to dissolve these 0.7 wt.% tablets. And the alloy was kept at 710 °C, after which the warmed (300 °C) Nichrome powder ($x\%$ wt., $x = 3\%, 6\%$) was poured at a rate of 1 gram per minute using the composite synthesizing set-up. For the in-situ generation of reinforcement Al_2O_3 by the interaction between matrix Al and NiCr Np, the composite was permitted to agitate for about 20 minutes [13–14]. The Al-4.5%Ti-1.5%C (TiC) master alloy was also introduced (0.5% wt.) with the reinforcement inserted composite to enhance the composite structure and increase its efficiency. Finally, the liquid metal reinforcement and alloy combination was put into a preheated (150 °C) frame. The difference strength was validated by the in-situ composite that was manufactured. Figure 1 depicts the mixing process throughout composite preparation.

3. RESULTS AND DISCUSSION

3.1. Analyzing the chemical composition

Table 2 shows the addition percentages of TiC in the in-situ prepared composites that were evaluated by using an optical emission spectrometer. The results clearly demonstrated that when the amount of NiCr Nps increases,

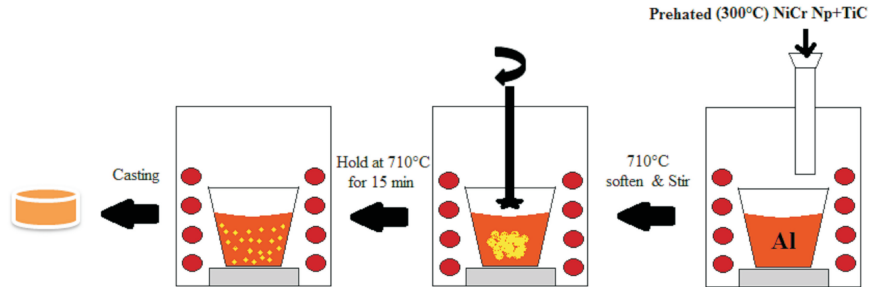


Fig. 1. Molten Aluminium in-situ technique

Table 2. The addition of TiC and grains sizes in prepared composites

Elements	A Specimen in the absence of TiC	A Specimen in the presence of TiC
Aluminum	96.5 at 3% of NiCr Np 93.0 at 6% of NiCr Np	96.40 at 3% of NiCr Np 94.50 at 6% of NiCr Np
Titanium	0.02 at 3% of NiCr Np 0.03 at 6% of NiCr Np	0.045 at 3% of NiCr Np 0.044 at 6% of NiCr Np
Silicon	0.75 at 3% of NiCr Np 1.00 at 6% of NiCr Np	0.800 at 3% of NiCr Np 0.800 at 3% of NiCr Np
Copper	1.60 at 3% of NiCr Np 3.50 at 6% of NiCr Np	1.800 at 3% of NiCr Np 3.200 at 6% of NiCr Np
Manganese	0.09 at 3% of NiCr Np 0.10 at 6% of NiCr Np	0.090 at 3% of NiCr Np 0.100 at 6% of NiCr Np
Magnesium	1.00 at 3% of NiCr Np 1.20 at 6% of NiCr Np	0.800 at 3% of NiCr Np 0.800 at 6% of NiCr Np
Chromium	0.13 at 3% of NiCr Np 0.12 at 6% of NiCr Np	0.750 at 3% of NiCr Np 0.130 at 6% of NiCr Np
Ferrum (iron)	0.13 at 3% of NiCr Np 0.80 at 6% of NiCr Np	0.130 at 3% of NiCr Np 0.730 at 6% of NiCr Np
Silicon	0.75 at 3% of NiCr Np 1.00 at 6% of NiCr Np	0.800 at 3% of NiCr Np 0.800 at 6% of NiCr Np
Nickel	0.05 at 3% of NiCr Np 0.04 at 6% of NiCr Np	0.040 at 3% of NiCr Np 0.070 at 6% of NiCr Np

the Al concentration falls as the Cu increases intensity. Furthermore, as compared to non-TiC composites, TiC has been proven to increase the value of Ti in composites.

Microstructural characterizations of a specimen

The microstructural characteristics of specimens were investigated using an optical microscope with image analysis.

3.2. Characterization of an AA 6061 + X NiCr composite (X=3%, 6%) in the absence of TiC

A metal matrix composite using AA 6061 aluminum alloy as the matrix and aluminum particulates as reinforcement was created by in-situ interaction of NiCr with heated AA 6061 without TiC. Figures 2 and 3 illustrate the optical microstructures of the in-situ composite generated by applying 3% NiCr and 6% NiCr, respectively, in the absence and non-additive of TiC under etching circumstances to detect the grain boundary.

In the structure, we can see alumina particles and the creation of grain boundaries. The generated intermetallic particles may also be seen in the microstructures. The production of alumina as well as the stages formed, such as NiAl_2 , have been observed. Grain results for the composite in the absence of TiC are calculated in Fig. 2, and the grain size is mostly about $100\text{ }\mu\text{m}$ – $350\text{ }\mu\text{m}$.

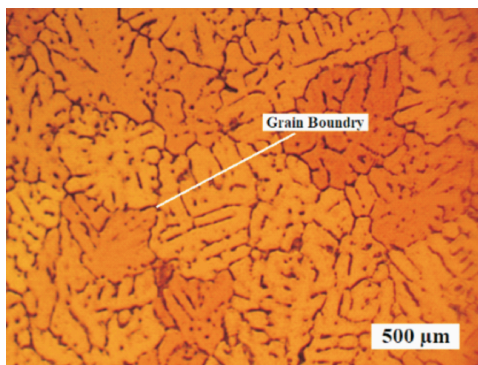


Fig. 2. AA 6061 + 3% NiCr Np in the absence of TiC

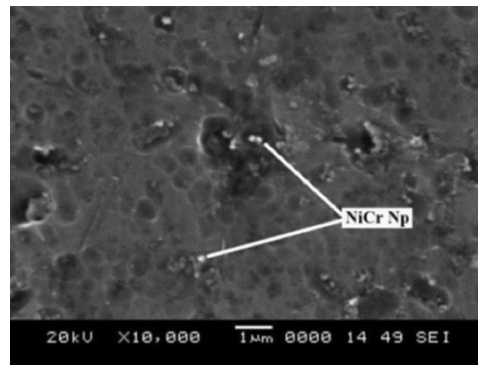


Fig. 3. AA 6061 + 6% NiCr Np in the absence of TiC

3.3. Characterization of an AA 6061 + X NiCr composite (X=3%, 6%) in the presence of TiC

The grain refiner Al-4.5Ti-1.5C master alloy (TiC) was introduced with %wt. to manufacture the 0.02%Ti within the in-situ composite that has al-

ready been manufactured in order to minimize grain size and boost characteristics. Figure 4 shows the microstructures of an in-situ composite containing 3% NiCr and TiC.

The TiC will diminish grain size from 80 μm –350 μm to 90 μm –100 μm as illustrated in Fig. 5. The grain boundaries are visible at a high magnification of 20X in the figures. Figure 4 illustrates the grain boundary of the composite casting sample, which has a grain size of roughly 30–60 μm , and also shows copper and pure Nichrome powder, which will increase the strength and hardness of the alumina particles generated. If the amount of NiCr was higher, it may be feasible.

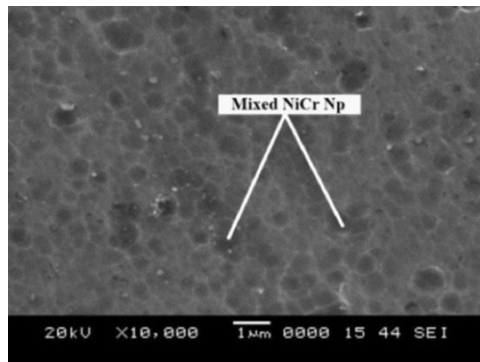


Fig. 4. AA-6061 + 6% NiCr
in the presence of TiC

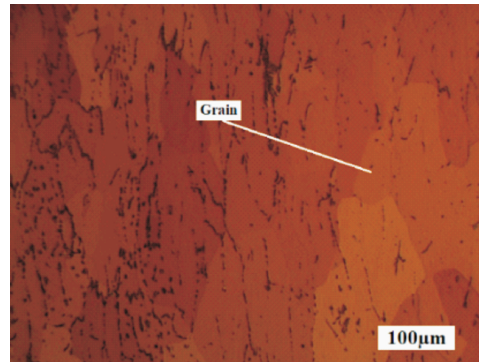


Fig. 5. AA 6061 + 3% NiCr
in the presence of TiC

Figure 4 illustrates the ring formed by the stage NiAl_2 inside of the composite during solidification. It is also possible to construct the shape that is plainly evident. The qualities of the casting may alter as a result of these two processes. The TiC created by adding Al-4.5Ti-1.5C functions as an excellent grain refiner for aluminum alloys, and the grain refinement is greatly enhanced when compared to castings in the absence of Al-4.5Ti-1.5C. In the absence and presence of Al-percent Ti-1C addition in the microstructure, this difference is clearly visible. The produced grains have average 90 micrometers in length.

3.4. Refinement of grain boundary and its enhanced values

The additions of TiC master alloy were the key factor in reducing grain size. We can enhance the qualities of the composite casting by lowering the grain size. The image analyzer coupled to the Leica optical microscope was used to determine the grain sizes. The average grain size values recorded while capturing microstructures using a Leica optical microscope with image

Table 3. The addition of TiC and grains sizes

% age of Nanoparticles	Grain size of sample in the absence of TiC	Grain size of sample in the presence of TiC
3% NiCr Nanoparticles	230 μm	95 μm
6% NiCr Nanoparticles	190 μm	50 μm

Table 4. Hardness values of specimen at different conditions

Specimen data	HV values at casting	HV values at heat treated
Absence of TiC with 3% NiCr Np	101.0	150.0
Presence of TiC with 3% NiCr Np	138.0	164.3
Absence of TiC with 6% NiCr Np	115.2	148.0
Presence of TiC with 6% NiCr Np	119.7	150.6

analyzer are listed in Table 3. The addition of TiC refines the grains and lowers their sizes, as shown by the results.

The addition of TiC to the composite resulted in a significant reduction in grain sizes, as seen in Fig. 6. This is mostly due to Titanium carbide nucleation. The grain size was initially 230 μm and was decreased to 95 μm with a little quantity of TiC. The grain size was also lowered by 3.8 percent wt. NiCr and TiC with a 50 μm value. Hardness will raise as particle size decreases.

The physical characteristics of metals are influenced by the size, shape, and arrangement of phases, as well as particle size. Precision microscopes with a magnification of roughly 500 X and a measuring precision of +0.4 microns were applied to calculate the indentations. Differences of +0.3 micrometers may generally be corrected to the same investigator. The composite was subjected to a Vickers hardness test to determine the hardness of the various stages. Table 4 shows the hardness values of composite samples under heat treated (fluid processed & time toughened) and as cast settings for different test samples. The link between hardness levels and sample type is also shown in Fig. 7. The samples were heated in solution for 3 hours at 550 °C before being aged for 7 hours at 180 °C. The findings reveal the production of very fine precipitates as well as an increase in strength and hardness. The inclusion of the master alloy Al-4.5Ti-1.5C enhanced the hardness of AA-6061, allowing tiny intermetallic particles to be released evenly throughout the melt and function as nucleating sites. These stable intermetallic particles serve to boost hardness and strength. As a result, the hardness results calculated from micro

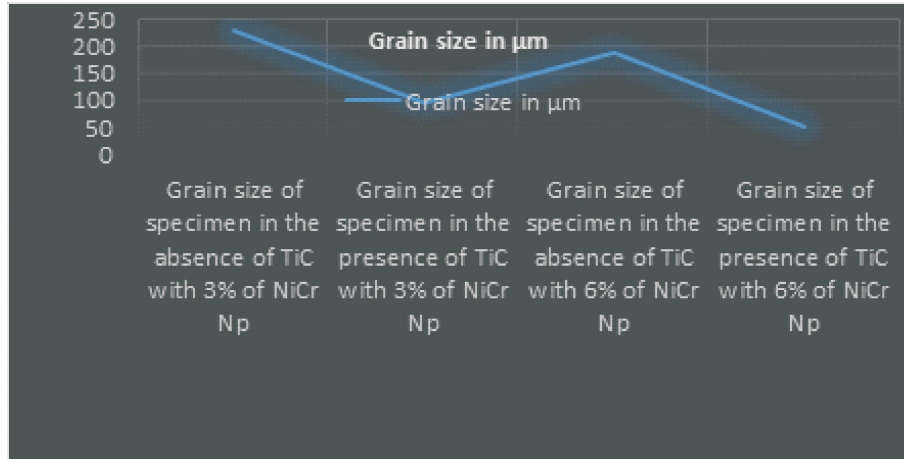


Fig. 6. Comparison of grain sizes

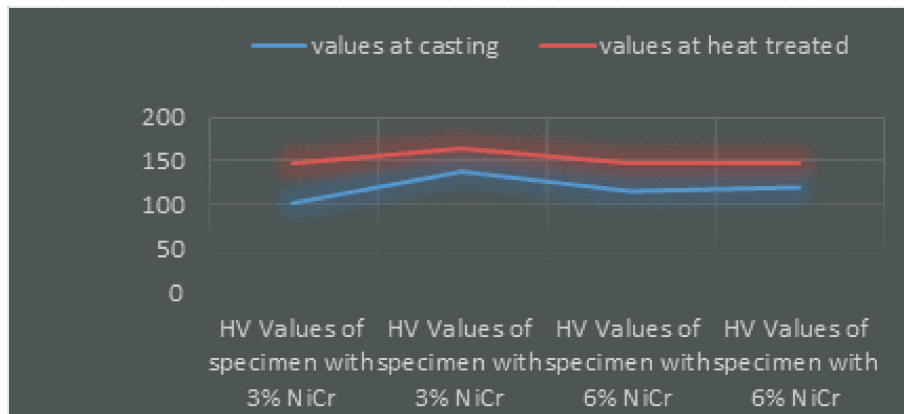


Fig. 7. Hardness values of specimen at different conditions

hardness testing show that adding Al-4.5Ti-1.5C master alloy to the materials would improve their qualities and raise their hardness value. The heat treatment procedure, along with solution treatment after aging treatment, raises the hardness value to 25 HV better than before. The Table 4 shows the hardness values of specimen at different conditions.

4. CONCLUSIONS

- i. In-situ fabrication of aluminum composite was accomplished.
- ii. The manufactured composite has the phases – Al_2O_3 , Mg_2Si , NiAl_2 , NiCr ,

and Ni. The mechanical characteristics of the castings are improved by the stages and Al_2O_3 .

- iii. The insertion of 0.4 percent TiC to the composite (through a master alloy addition of Al-4.5Ti-1.5C) decreases grain size and raises hardness values from 141 HV to 166 HV.
- iv. By nucleating particles, TiC serves as a grain refiner and raises the strength and hardness characteristics. Hardening at 180°C for 7 hours.
- v. When compared to samples that have not been aged, the hardness value following solution treatment is roughly 25 HV–35 HV.

STATEMENTS AND DECLARATION

- Funding: All budgetary funds come from key R&D projects in Gansu Province to ensure the smooth development of research work exhibition.
- Conflicts of Interest: The authors declare no conflict of interest.
- Institutional Review Board Statement: Not applicable.
- Informed Consent Statement: Not applicable.
- Data Availability Statement: Data will be provided upon reasonable from the corresponding author. No new data were created or analyzed in this study. Data sharing is not applicable to this article.

ACKNOWLEDGEMENTS

We appreciate the technical help provided by Lanzhou University Technology's School of Material Science and Engineering in Lanzhou, Gansu Province, China, especially my supervisor Dr. Ding Wanwu who has great contribution in the current research.

REFERENCES

- [1] N. BHARAT AND P. S. C. BOSE, An Overview of Production Technologies and Its Application of Metal Matrix Composites, *Advances in Materials and Processing Technologies* (2021), <https://doi.org/10.1080/2374068X.2021.1878707>.
- [2] M. FARAS *et al.*, Introduction to Powder Metallurgy: A Review, *IAR Journal of Engineering and Technology* (2021) **2** (3) 1–7, ISSN: 2708-5155, e-ISSN: 2708-5163.
- [3] C. KARLA, *et al.*, Processing and Characterization of Hybrid Metal Matrix Composites, *Journal of Materials and Environmental Sciences* (2018) **9** (7) 1979–1986, ISSN: 2028-2508.

- [4] A. KUMAR, *et al.*, Fabrication Methods of Metal Matrix Composites (MMCs), *Materials Today: Proceedings*, Elsevier (2021) **46** (15) 6840–6846, ISSN: 2224-7853.
- [5] T. YESHIYE AND M. GIZAW, A Review on Effects of Reinforcements on Properties and Wear Behaviour of Aluminium Metal Matrix Material, *International Journal of Research in Engineering Technology* (2021) **6** (2), ISSN: 2455-1341.
- [6] A. PATIL, *et al.*, Tribological Behavior of Carbon-Based Nanomaterial-Reinforced Nickel Metal Matrix Composites, *Materials* (2021) **14** (13) 3536, DOI: 10.3390/14133536.
- [7] S. YU, *et al.*, The Grain Growth and Boundary Evolution of Extra-Coarse-Grained Cemented Carbides by Pressureless Sintering of Ball-Milling-Mixed WC with Co at Different Temperature, *Materials Characterization*, Elsevier (2021) **180** 111386, <https://doi.org/10.1016/j.matchar.2021.111386>.
- [8] D. S. ATEPHEN AND P. SETHURAMALINGAM, An Application of Fuzzy Logic with Grey Relational Technique in Grinding Process Using Nano Al₂O₃ Grinding Wheel on Ti-6Al-4V Alloy, *International Journal of Machining and Machinability of Materials* (2021) **23** (1) 21–46.
- [9] T. ZHANG, *et al.*, Study on the Al₂O₃p/Al composites prepared by Al-calcined kaolin system, *Materials Science and Technology* (2021) **37** (6) 632–642, <https://doi.org/10.1080/02670836.2021.1939486>.
- [10] T. SINGH, S. TIWARI, AND D. SHUKLA, Influence of Nanoparticle Addition (TiO₂) on Microstructural Evolution and Mechanical Properties of Friction Stir Welded AA6061-T6 Joints, *Advances in Production and Industrial Engineering*, Springer (2021) 219–228.
- [11] H. SINGH, *et al.*, The role of In-situ Ceramic Reinforcements on Microstructure Evolution and Mechanical Properties on Developed Hybrid Mg-MMCs, *Materials Science and Engineering: A*, Elsevier (2020) **789** 139577, <https://doi.org/10.1016/j.msea.2020.139577>.
- [12] C. GAO, *et al.*, Selective laser melting of TiN nanoparticle-reinforced AlSi10Mg composite: Microstructural, interfacial, and mechanical properties, *Journal of Materials Processing Technology* (2020) **281** 116618, DOI: 10.1016/j.jmatprotec.2020.116618.
- [13] A. Y. NALIVAIKO, *et al.*, Al–Al₂O₃ powder composites obtained by hydrothermal oxidation method: Powders and sintered samples characterization, *Journal of Alloys and Compounds* (2020) **825** 154024, DOI: 10.1016/j.jallcom.2020.154024.
- [14] DAHA, M., *et al.*, Mechanical and Tribological Characterization of a Novel Hybrid Aluminum /Al₂O₃/RGO Composite Synthesized Using Powder Metallurgy, *Journal of Materials Engineering and Performance* (2021) **30** (4) 2473–2481.

Received March 10, 2022